



The Development of a Hybrid Thermoplastic Ballistic Material With Application to Helmets

by Shawn M. Walsh, Brian R. Scott, and David M. Spagnuolo

ARL-TR-3700

December 2005

NOTICES

Disclaimers

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

Citation of manufacturer's or trade names does not constitute an official endorsement or approval of the use thereof.

DESTRUCTION NOTICE—Destroy this report when it is no longer needed. Do not return it to the originator.

Army Research Laboratory

Aberdeen Proving Ground, MD 21005-5069

ARL-TR-3700**December 2005**

The Development of a Hybrid Thermoplastic Ballistic Material With Application to Helmets

Shawn M. Walsh, Brian R. Scott, and David M. Spagnuolo
Weapons and Materials Research Directorate, ARL

| REPORT DOCUMENTATION PAGE | | | | Form Approved OMB No. 0704-0188 | |
|---|-----------------------------|------------------------------|--|--|---|
| <p>Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.</p> <p>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</p> | | | | | |
| 1. REPORT DATE (DD-MM-YYYY) December 2005 | | 2. REPORT TYPE Final | | 3. DATES COVERED (From - To) September to October 2005 | |
| 4. TITLE AND SUBTITLE The Development of a Hybrid Thermoplastic Ballistic Material With Application to Helmets | | | | 5a. CONTRACT NUMBER | |
| | | | | 5b. GRANT NUMBER | |
| | | | | 5c. PROGRAM ELEMENT NUMBER | |
| 6. AUTHOR(S) Shawn M. Walsh, Brian R. Scott, and David M. Spagnuolo (all of ARL) | | | | 5d. PROJECT NUMBER 622618.H80 | |
| | | | | 5e. TASK NUMBER | |
| | | | | 5f. WORK UNIT NUMBER | |
| 7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army Research Laboratory Weapons and Materials Research Directorate Aberdeen Proving Ground, MD 21005-5069 | | | | 8. PERFORMING ORGANIZATION REPORT NUMBER ARL-TR-3700 | |
| 9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) | | | | 10. SPONSOR/MONITOR'S ACRONYM(S) | |
| | | | | 11. SPONSOR/MONITOR'S REPORT NUMBER(S) | |
| 12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution is unlimited. | | | | | |
| 13. SUPPLEMENTARY NOTES | | | | | |
| 14. ABSTRACT U.S. helmet material technology has changed relatively little since the introduction of aramids in the 1970s. All U.S. Army ballistic helmets use woven aramids with a thermoset (toughened phenolic) resin system. The current research explores the use of thermoplastic (polyolefin-based) matrix material. Although thermoplastic aramid systems have been evaluated for specialty applications, they have often failed to meet all the stringent criteria required of a U.S. Army helmet system. The present work seeks to remedy this by investigating hybrid ballistic material solutions. The combination of mass efficient ballistic and independent structural materials provides a means of meeting the spectrum of performance requirements demanded by U.S. Army helmet specifications. In addition to this, a series of helmet prototypes has been produced, which explore alternate design methods for selectively stiffening the core ballistic shell. Preliminary normalized performance data are presented that demonstrate the improved mass efficiency of the hybrid ballistic material solutions. This work summarizes the U.S. Army Research Laboratory's initial development of a candidate ballistic material solution to meet the Future Force Program requirements. | | | | | |
| 15. SUBJECT TERMS aramid; composite armor; helmets; protection; thermoforming; thermoplastics | | | | | |
| 16. SECURITY CLASSIFICATION OF: | | | 17. LIMITATION OF ABSTRACT SAR | 18. NUMBER OF PAGES 37 | 19a. NAME OF RESPONSIBLE PERSON Shawn M. Walsh |
| a. REPORT Unclassified | b. ABSTRACT Unclassified | c. THIS PAGE Unclassified | | | 19b. TELEPHONE NUMBER (Include area code) 410-306-0815 |

Contents

| | |
|--|-----------|
| List of Figures | iv |
| List of Tables | iv |
| Acknowledgments | v |
| 1. Introduction | 1 |
| 2. Background | 1 |
| 3. Helmet Design and Material Considerations | 7 |
| 3.1 Ballistic Resistance..... | 7 |
| 3.2 Transient Deformation | 8 |
| 3.3 Static and Dynamic Structural Performance and Stability..... | 9 |
| 3.4 Human Factors and Other Considerations..... | 9 |
| 4. Thermoplastic Based Helmet Materials, Specimens, and Helmets | 10 |
| 4.1 Thermoplastic Aramid Systems | 10 |
| 4.2 Specimen Preparation and Fabrication..... | 10 |
| 4.3 Mechanical Characterization..... | 11 |
| 5. Helmet Manufacturing Considerations | 12 |
| 5.1 Series Fabrication | 13 |
| 5.2 Parallel Fabrication..... | 13 |
| 6. Results and Discussion | 14 |
| 6.1 Flat Plate Fabrication and Results | 16 |
| 6.2 Helmet Design Variations | 17 |
| 6.2.1 Monolithic KM2 Shell-Polyolefin Shell | 17 |
| 6.2.2 Graphite Skin on Polyolefin-KM2 Shell | 18 |
| 6.2.3 Polyolefin-KM2 Encapsulated by Thermoplastic Graphite | 18 |
| 6.2.4 Integrally Stiffened Polyolefin-KM2 Shell | 19 |
| 7. Conclusions | 19 |
| 8. References | 20 |
| Distribution List | 21 |

List of Figures

| | |
|--|----|
| Figure 1. Historical perspective of U.S. Army helmet design and materials..... | 2 |
| Figure 2. Transition of new helmet materials. | 6 |
| Figure 3. Current and a future U.S. Army helmet systems..... | 6 |
| Figure 4. Coupling of headgear and body-borne systems..... | 7 |
| Figure 5. Weapons interface evaluation of prototype headgear. | 9 |
| Figure 6. Still photographs from high speed digital imaging of thermoplastic-aramid panel. | 10 |
| Figure 7. An integrated, low scrap and low cost semi-automated hybrid helmet process..... | 12 |
| Figure 8. A comparison of series and parallel fabrication cycles for hybrid helmet manufacture..... | 14 |
| Figure 9. A comparison of monolithic and hybrid (IM7 graphite) thermoplastic KM2..... | 15 |
| Figure 10. Applicability of new helmet recipes to current and future helmet systems. | 16 |
| Figure 11. ARL recipe. | 17 |
| Figure 12. Monolithic shell composed of KM2-polyolefin. | 18 |
| Figure 13. Graphite-epoxy on outer surface of KM2-polyolefin shell. | 18 |
| Figure 14. KM2-polyolefin fully encapsulated by graphite-nylon. | 19 |
| Figure 15. Integrally stiffened KM2-polyolefin shell..... | 19 |

List of Tables

| | |
|--|----|
| Table 1. Comparison of current and proposed helmet manufacturing methods. | 12 |
| Table 2. Mechanical data for monolithic and hybrid recipes..... | 15 |
| Table 3. A comparison of PASGT and hybrid shell materials. | 17 |

Acknowledgments

The authors gratefully acknowledge the generous support of Mr. Matthew Correa and Mr. David Krasnecky under the Natick Soldier Center-led Future Force Warrior (FFW) Program, as well as internal U.S. Army Research Laboratory support from Mr. Thomas Haduch, principal investigator of the personnel protection work area. The authors also wish to thank Artisent, Inc., for supplying design and tooling versions of the FFW helmet, and Diaphorm LLC (Limited Liability Company) for their excellent technical support. Finally, we would like to recognize the outstanding efforts of our visiting summer students John Cook, Alvin Lim, and Gregory Teitelbaum, for their assistance in material preparation, fabrication, and assembly.

INTENTIONALLY LEFT BLANK

1. Introduction

U.S. Army transformation is one of the largest efforts in modern times to reshape the overall structure and function of ground forces. It is designed to respond to a host of new and emerging threats, and it explicitly recognizes the need for and vulnerability of electronically based systems on and off the battlefield. Indeed, U.S. Army transformation features the Future Combat Systems (FCS), which is a “system of systems.” The prominent theme in this new reshaping of the Army is emphasis on strategically arraying and integrating as many technologies together to provide an overwhelming and decisive advantage in hostile environments.

The emergence of electronics on the battlefield has been incremental. The impact of this is being re-thought as part of the U.S. Army transformation. The goal is not only to ensure overall integrated system effectiveness but to minimize any potential weight and human performance penalties associated with incorporating this technology on and around the Soldier. Many mobile electronic systems bring a concomitant requirement for power, and thus battery weight and efficiency, together with other novel power-generating and storage technologies, are a key focus of Army transformation goals.

The addition of state-of-the-art electronics systems and power systems has stimulated a total redesign of the overall Soldier system ensemble. The goal is to provide an effective, flexible, and lightweight system that enables the Soldier to rapidly and successfully do his or her mission. The challenge is integrating the lethality, survivability, and other technologies onto the Soldier without causing the overall system weight to impede the Soldier’s ability to execute a wide variety of tasks.

New designs for the Soldier-borne uniform and equipment are being developed, tested, and revised, based on a variety of human factors and other types of testing. Key to this system development is the use of alternate materials to shed weight from conventional systems. The U.S. Army transformation has provided a stimulus for pushing the limits of conventional materials and has opened the opportunity for the consideration of new materials and material combinations. These materials may also include hybrids to maximize the overall system performance while minimizing weight.

2. Background

Helmet materials and designs have evolved primarily in light of prevailing threats and the invention of new and improved ballistic materials. Figure 1 is a basic summary of U.S. helmet designs and materials since World War (WW) I. For example, the helmet designs in WW I were

significantly different than in WW II. WW I was characterized by an unprecedented amount of trench warfare, and the hot, sharp debris falling from relatively high angles was typical. This gave rise to the fairly wide “brim” that gave the WW I helmet its distinctive look.

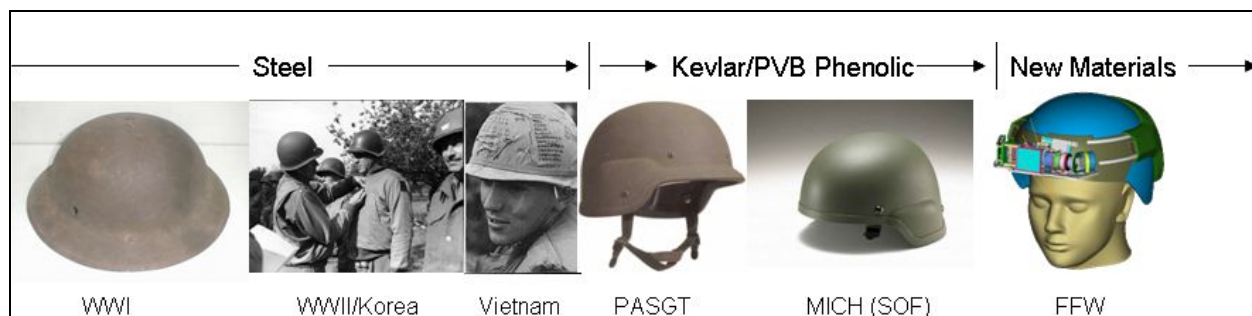


Figure 1. Historical perspective of U.S. Army helmet design and materials.

Ballistic helmets today reflect combat experiences learned from WW I to contemporary deployments of personnel and equipment. With the advent of trench warfare, fragmentation from exploding ordnance was the predominant source of injury and death to troops on the front line. The randomness of the shrapnel threat forced the design of protective head gear to cover not only the very top but also the sides, front, and back of the Soldier’s head. The original French and British designs of WW I were adapted by the U.S. Army and involved formed Hadfield steel bowls with web-based suspensions. Weight, comfort, and protection level influenced the eventual redesign of the fragmentation helmet to become the famous M1 helmet of WW II. This steel outer shell used a molded inner shell to attach the suspension made of cotton webbing and leather. The composite inner liner nested into the ballistic steel shell. The inner liner, introduced in 1941, was made of cotton fabric-reinforced phenolic laminate. An improved ballistic version of the liner, fielded in 1961, used nylon fabric to replace the cotton. The combined shells provided higher protection levels over a greater coverage area than the previous M1917 copy of the British Mk I “Brodie” helmet of WW I. The one-size M1 helmet weighed 1.55 Kg, had 0.12 square meter of surface coverage, and protected against the 0.45 caliber round at 244 m/s with a 50% ballistic limit of 396 m/s against the standard NATO (North Atlantic Treaty Organization) 1.1-gram fragment simulator.

In the early 1960s, the U.S. Army embarked on an experimental effort to replace this two-part helmet design with a single-walled, lighter and more protective configuration. Composite materials were considered because of their known higher ballistic efficiencies. Glass fiber and nylon reinforcements were evaluated in the same toughened phenolic as was used in the earlier liners. With the invention of Kevlar¹ in 1965, it became immediately obvious that what could be done with nylon would be done better with this high strength polymer. Kevlar was commercially available in 1972, with the U.S. Army already evaluating it late in the 1960s. As is most often the case, a direct substitution of the newer, stronger fiber from the previous one showed less-than-optimal improvement. With considerable development effort, the “steel pot” M1 helmet

¹Kevlar is a registered trademark of E. I. DuPont de Nemours & Co., Inc.

was gradually eliminated from the U.S. inventory in the late 1970s and replaced with the improved Kevlar design called the Personal Armor System for Ground Troops (PASGT) in 1976 (1). The PASGT originally had three sizes, now four. Throughout the development, improvements in protection level (50% ballistic limit now 610 m/s), area of coverage (0.14 square meter) and better fit (1st to 99th percentile of the U.S. military population) were achieved while the same weight was maintained as for the M1.

The PASGT has found much praise from the troops; it has saved many lives, including the civilian police forces who have now adapted it. It has proved itself in field use, which suggests that its durability is also adequate. The laminated material from which it is formed is not ideal structurally, however. A low resin content (roughly 20% by weight), multi-ply fabric architecture and high porosity was selected primarily for its ballistic attributes, and one would expect that it could exhibit problems with durability or blunt trauma (lower flexural rigidity would suggest more deflection and lower structural capacity). With its standard wall thickness of 9 mm, it barely meets the practical requirements.

Since this very successful introduction, the desired trend has been related to weight reduction. Complaints related to comfort, hearing acuity, and relative motion or mobility and the desire to mount additional devices as noted earlier have required the shell material to provide equivalent protection at reduced weight. Research into higher efficiency materials has moved toward more compliant laminates with stronger reinforcements. The advanced combat vehicle crewman (ACVC) helmet was fielded in the late 1980s with less coverage but equal protection at reduced weight where it did cover. The U.S. Army type classified this new helmet material with the newest Kevlar KM2 fiber (2), but several design details were also changed. Besides the shell thickness being reduced to 7.6 mm, the fiber denier was reduced, the fabric style changed, the ply count increased, and fabric interface was adjusted to include a fluoropolymer coating. The amount and type of laminating resin remained the same, but the overall trend was toward higher compliance of the final laminate. The KM2 fiber was stronger and tougher than the previous Kevlar 29 fiber. It is believed that both of these changes resulted in the higher performance. The identical material modification was evaluated for replacement of the PASGT and actually followed through the necessary evaluation cycle but was not selected for major procurement because significant weight reduction was less than perceived (15%). Its field durability has not been demonstrated to the same extent as PASGT.

Beginning in the early 1990s, the desire was to reduce the weight of the PASGT by at least 25%. The U.S. Marine Corps started a development program that evaluated several candidate materials with higher ballistic efficiency. Materials such as Spectra Shield² or Kevlar Mark III³ used alternate resin systems, fiber materials, or laminate architectures. Both were successfully molded into PASGT geometry and found to meet the ballistic and weight goals. Both failed to address the less-defined durability requirements, largely because of the higher flexural

²Spectra Shield is a registered trademark of Honeywell.

³DuPont proprietary coated fabric prelaminated material

compliance of either material. Brief attempts to resolve the structural limitations were not able to satisfy the program schedule, but initial ideas to make the final structure a hybrid with structural skins or rib reinforcement were proposed.

Since then, two new helmets have been produced for the U.S. military. The first is now called the advanced combat helmet (ACH) and was previously provided by the Army for special operations as the modular integrated communications helmet (MICH). This helmet uses a higher strength Kevlar K129, lower content phenolic resin (thus higher fiber content for the same weight), modified edge cut for lower protection surface, and a new suspension system for better comfort and possibly trauma reduction. With a shell thickness of 7.8 mm and lower resin content, it will have higher structural compliance and potentially the same limitations of the earlier lightweight helmets. The other helmet in current U.S. production is the new lightweight Marine Corps helmet. This helmet uses a higher strength fiber, Twaron⁴, with properties similar to Kevlar 129, and with the same phenolic resin, is expected to perform ballistically and structurally similar to the ACVC material described earlier. The geometry is the same as the PASGT, but the wall thickness is less, so the overall performance is similar to the lightweight PASGT.

The future in helmet design may follow what we are describing in this report. The Kevlar Mark III and Spectra Shield materials noted before involve thermoplastic resin matrices and are relatively flexible. If the ballistic requirements at reduced weight can be met with these materials, then future development efforts will likely focus on meeting the structural (durability) and trauma (transient deflection) constraints. Hybridization with structural skins is logical and should have a high probability of success. How to manufacture finished helmets from these new material systems in a practical, cost-efficient manner also remains to be demonstrated. One such example is with the Tepex⁵ (3) system now in production for the Norwegian military. Claims are made of complete molding cycles of less than 5 minutes, without the need of extensive hand pre-forming. Certainly the existing manufacturing infrastructure will have a significant influence in defining the initial capital investment and subsequent unit cost. What may be of particular interest is how to modify existing production equipment to allow for the thermoforming of thermoplastic matrix composite materials. Identifying the proper combination of fiber, resin, reinforcement architecture, and manufacturing process for specific requirements is the goal of our present study. Some trends have already been identified. Beyond the increased compliance, we know that higher ply count and lower basis weight layers will improve ballistic efficiencies. Reducing the frequency of cutting and tacking will increase effective fiber length but will introduce wrinkling issues. Lowering the resin content or weakening the resin-fiber interface will promote delamination and deflection which introduce positive and negative attributes. Through-the-thickness reinforcement will similarly control the extent of the deflection. The most obvious parameter is the ratio of ballistic to structural material used in any hybrid architecture. The orientation of each is also a variable. Fabric architectures that allow for

⁴Twaron, which is a registered trademark of Teijin, is a synthetic fiber made from aramid polymer.

⁵Tepex is a registered trademark of Bond-Laminates GmbH, Germany.

conformal draping without tacking is highly desirable, but the amount of necessary in-plane distortion may have limitations.

Certainly as new high strength reinforcement fibers are introduced, they need to be evaluated in this ballistic application. It is somewhat universally agreed that higher specific strength fibers with sufficient toughness (strain energy capacity or high elongation) should be good candidates for lighter weight helmets. Newer polymers such as pyribenzamine (PBO⁶), MePPD-TA (4) or M5⁷ (5) may suggest great potential but may exhibit other limitations or may simply not be commercially available. The resin systems may also exhibit similar limitations, especially around thermal stability and environment degradation. In addition to the subject areas of structure and ballistics noted already in this report, the practical issues around cost, availability, and environmental susceptibility will ultimately factor into what materials are good candidates to replace the incumbents.

There are a number of promising materials on the horizon, most notably a relatively new organic fiber with a complex molecular structure known as M5 (6). M5 is attractive based on initial properties (strength 4 GPa, modulus 330 GPa, and elongation 1.5%). However, to date, M5 has been produced in only small, laboratory production runs. There are still significant issues to resolve. Even when M5 does become commercially available in sufficient quantities, it will likely be expensive, given the capital investment and development costs. As such, the U.S. Army Research Laboratory (ARL) has proposed an incremental approach that will first establish thermoplastics and thermoplastic-based matrices as viable candidates for fabricating helmet shells. The advantage of this approach is the ability to reap the near-term benefits of commercially available thermoplastic matrix aramids, such as Tepex (3) and Mark III as well the ability to “spiral in” new fibers such as M5 (figure 2).

The Future Force Warrior (FFW) is a major element of the Army transformation. FFW is responsible for defining not only the type of materials, equipment, and systems that the Soldier will wear and use but also the hardware and software necessary for the Soldier to be part of a larger “network.” Current Soldiers configure their equipment, depending on the mission (figure 3a). While this flexibility is desirable, a major problem with this approach is the tendency to burden the Soldier with too many discrete systems. Such systems include IR cameras mounted on the helmet, communication devices on the side of the helmet, and so on. FFW is focused on streamlining these functions by determining what hardware is to be integrated into or onto a helmet as well as those devices that will be modular in nature. More importantly, FFW is focused on redesigning a helmet that allows for optimal integration and modularity, as shown in figure 3b.

⁶PBO (ZYLON) is a new high-performance fiber developed by TOYOBO; ZYLON is a registered trademark of TOYOBO and consists of rigid rod chain molecules of poly(p-phenylene-2,6-benzobisoxazole)(PBO).

⁷poly{2,6-diimidazo[4,5-b:4',5'-E]pyridinylene-1,4-(2,5-dihydroxy)phenylene}

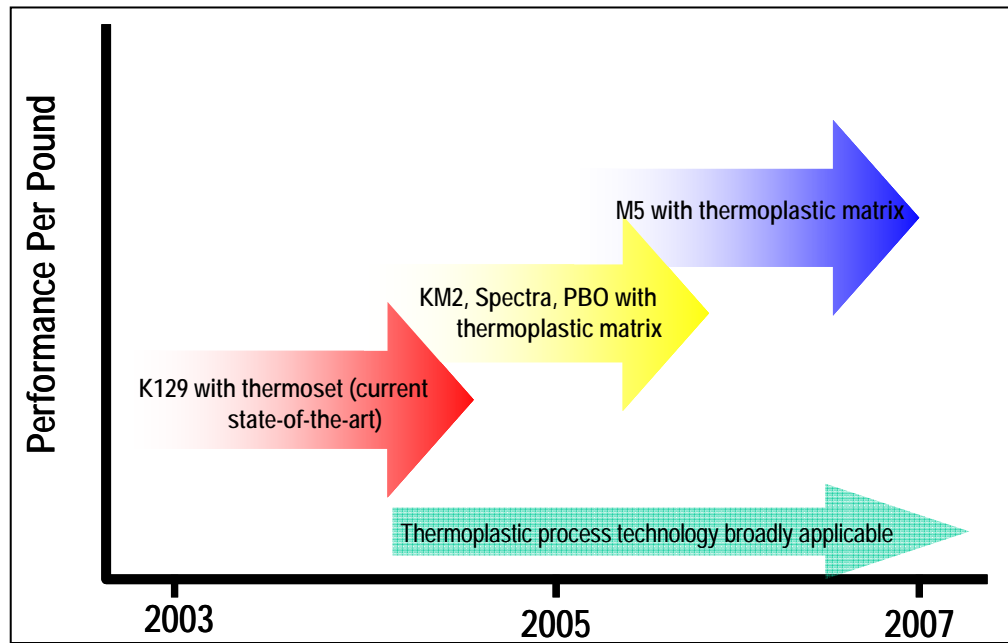


Figure 2. Transition of new helmet materials.



Figure 3. Current and a future U.S. Army helmet systems.

The new helmet architecture, together with the integrated electronic sensors and other devices, will demand a balance between the enhanced functionality and the overall weight of the helmet. Indeed, in the FFW program, the helmet is now referred to as “headgear” and as such implies a system rather than materials or assembly of discrete components. Furthermore, the FFW ensemble is divided into two basic parts: “neck up” which includes all the systems and functions associated with the headgear, and “neck down,” which encompasses the uniform and other equipment attached to the Soldier’s body and extremities. An early prototype of this type of integrated system, known as Scorpion, is shown in figure 4. Weight reductions will be achieved in at least two ways. The first is by shrinking the active devices by further miniaturizing the

electronics, power, and packaging of these sub-systems. The second will be in developing materials (and combinations of materials) that will enable weight reductions in the helmet shell, suspension system, comfort liners, etc. The design and material selection for the FFW headgear is a highly coupled process, especially when one considers the physical linkages to neck-down systems.

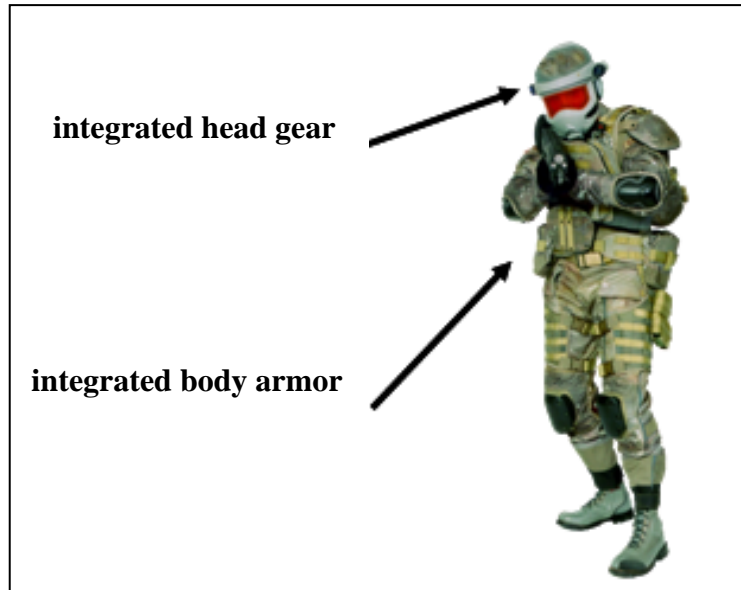


Figure 4. Coupling of headgear and body-borne systems.

3. Helmet Design and Material Considerations

3.1 Ballistic Resistance

The primary goal of the helmet shell is to protect the Soldier from a variety of threats. First, the requirement is to limit the perforation of fragments or bullets through the helmet. Even if the fragment is stopped, the deflection of the shell can engage the skull and cause injury. The current PASGT uses an effective air gap of approximately 13 mm between the inner shell wall and the Soldier's head to accommodate any deflection during projectile arrest. Deflections greater than this will likely engage the skull, but whether this engagement is lethal is unclear. Recent studies at the University of Virginia and Natick Soldier Center, Massachusetts, have suggested that there is a threshold of impulse or force that is likely to cause serious trauma. An alternate test protocol is proposed that would measure such an impulse delivered to the skull during controlled test conditions. It is obvious that lower impulse and extent of deflection is desirable in order to minimize the probability of death.

The current study described in this report simply measures the relative amount of free field deflection in a consistent impact loading condition. We are using high speed video techniques to measure the peak deflection during the arrest of a 1.1-gram fragment simulator at an impact velocity just below the limit velocity of the candidate material system. This testing has been performed on flat plate samples with partial lateral support. Whether this configuration can be related to the needed trauma requirement is uncertain. We can surely identify relative differences in the extent of transverse deflections for various material combinations and quantify the relative trade-offs among weight, structural durability, and the extent of lateral deflection.

The general method for characterizing a material's ballistic performance is to conduct a V_{50} ballistic test. A V_{50} is defined as the velocity at which there is an equal probability of a partial or a complete perforation for the given armor and threat. Security classification becomes critical when both the threat and armor are discussed or presented simultaneously, especially if the mass efficiency of the armor is significant. Screening monolithic and hybridized materials can be a lengthy and costly undertaking, given that an extensive amount of data needs to be generated in order to build requisite confidence in the performance of a given ballistic material "solution." As such, researchers tend to choose threats that are known to be difficult to defeat, such as small fragments at high speed. Bullets such as the 9 mm are also difficult to arrest with particular challenge of the transient deflections from the relatively large mass of the 9-mm projectile. Note that Europe tends to emphasize a 1.1-gram fragment simulator rather than a 1-gram right circular cylinder surrogate. In general, the required V_{50} for U.S. fragment simulators is higher than that required by European standards. Ballistic testing can be complicated by hot and cold testing requirements. Thermoplastics, for example, tend to soften at higher temperatures. This softening can translate into improved ballistic performance; however, it can also undesirably increase the transient deformation and reduce the structural rigidity of the helmet.

3.2 Transient Deformation

Transient deformation is a direct result of the kinetic energy being dissipated within the ballistic material. It is concomitant with the ballistic impact and it plays a very significant role in determining the design and materials selection of a helmet system. Fabrics, although extremely ballistically resilient at areal densities around 0.975 gram per square centimeter, tend to deform significantly. The fragment or bullet could conceivably be arrested by the fabric, but the resulting deformation could still result in a fatal injury by adversely engaging the skull. By contrast, thermoset composites such as polyvinylbutyral (PVB) phenolic-aramid systems reduce the transient deformation, even though their ballistic performance may be less than that of a pure fabric system. Thermoplastic composite materials offer a compromise of fabric and thermoset composite performance. That is, the thermoplastic tends to deform but not as much as pure fabric, and it tends to have better ballistic resistance than a thermoset-based composite material.

3.3 Static and Dynamic Structural Performance and Stability

Practical durability is a necessary trait for any article used in combat. Helmets must also pass static structural tests as well. “Ear-to-ear” loads of 2000 to 3500 kPa must be withstood by the helmet for several cycles without any permanent deformation of the helmet structure. Thermoset composites tend to do well, given the higher matrix modulus (as compared to a thermoplastic matrix). It is expected that the trends we identify for structural stiffness will track what we observe with the extent of transient lateral deformation. One exception to this correlation is obvious. If the material combination behaves in a brittle fashion (low tensile strength at high rates of loading), then it is possible that if brittle failure occurs prematurely, inelastic deflection will dominate and not necessarily track what we observe in the low rate structural testing. That is one strong argument for performing both types of tests on all material candidates. One additional comment: the transient testing ought to be performed at full scale because of the uncertainty of temporal scaling of the ballistic event.

3.4 Human Factors and Other Considerations

Comfort, hearing, weight distribution, and a host of other factors also influence design and material selection of a typical helmet. Many of these factors are weighted evaluations through models and experimental testing to reveal possible issues or concerns with the helmet system. For example, using a spiral design cycle strategy, researchers are constantly refining the design of attachments so that they optimize interfacing with weapons (figure 5) while still providing the desired electronic communication and optical systems in an ergonomically and mass-efficient design.



Figure 5. Weapons interface evaluation of prototype headgear.

4. Thermoplastic Based Helmet Materials, Specimens, and Helmets

4.1 Thermoplastic Aramid Systems

During the development of an effective thermoplastic-based aramid ballistic recipe, it was determined that transient deflection quickly becomes the limiting factor. To preserve the ballistic benefits of thermoplastic matrix aramid systems and minimize the potential for such skull trauma, it will very likely be necessary to combine them with other materials that exhibit greater stiffness against static and dynamic loading. The notion of composite hybrids is hardly new; the challenge becomes delivering the desired level of protection and performance in the overall shell without adding significant weight.

Thermoplastic matrix aramid systems have excellent, mass-efficient ballistic properties. However, the thermoplastic matrix is typically 30% to 60% less rigid than even toughened thermoset (e.g., phenolic) matrix. This has significant implications for the overall static structural stability and resilience of the thermoplastic aramid shell, as well as the dynamic deflections associated with a ballistic event. To illustrate this phenomenon, consider figure 5. A Phantom v.7 high speed digital camera was used to capture the effects of a simulated ballistic fragment impact on the back side of a flat thermoplastic-aramid panel. This panel had an areal density that was nearly 50% of that recommended for producing a helmet shell. As can be seen in the sequence of images, the fragment is effectively contained and stopped but not before it induced significant deformation to the overall panel. A thermoplastic-Kevlar shell at this low areal density may be well suited for certain applications, but given that the deformation was well over 1 inch, it could cause severe skull fracture (and possibly death).

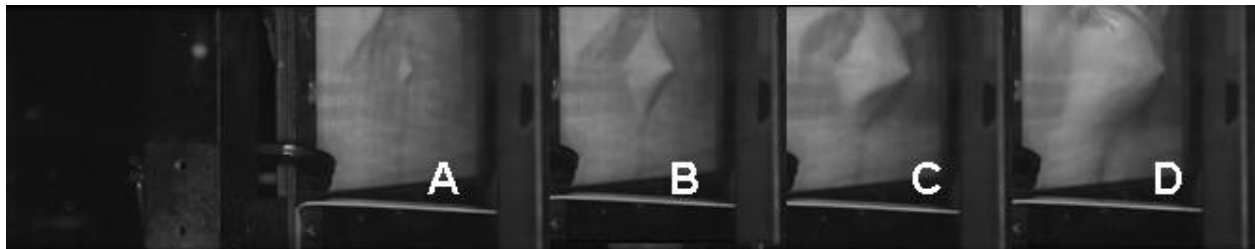


Figure 6. Still photographs from high speed digital imaging of thermoplastic-aramid panel.

4.2 Specimen Preparation and Fabrication

The design goal was to obtain an areal density of 1.75 pounds per square foot (psf) for all Kevlar-thermoplastic panels. Therefore, based on material and construction (i.e., unidirectional, plain weave, etc.), a ply orientation scheme was determined from which we obtained a preliminary weight for the skins. From there, the number of plies of Kevlar-thermoplastic was determined to obtain the 1.75-psf areal density.

The plies were cut into 15-inch square dimensions with the use of rotary shears made by Eastman Machine Co. The plies were then carefully stacked individually to assure proper alignment and to avoid ply sliding in the press (150-ton heat press, model MTP-24 made by Tetrahedron Associates, Inc.) with the thermoplastic side facing up. The last Kevlar-thermoplastic ply was reversed to provide better adhesive properties. The thermoset skin(s) were placed on the last ply. Teflon⁸ textured release film was placed between the top and bottom plies and the call plates, which contacted the heated platens. The press cycle used was 300 °F at 500 psi for 60 min and then cooled under pressure to approximately 80 °F. Differential scanning calorimetry (DSC) showed that the 250 °F thermoset “prepregs” were fully cured, and dwell times could be reduced from 60 minutes to 10 minutes, if preferred.

4.3 Mechanical Characterization

These candidate materials not only need to perform well ballistically but must also possess certain mechanical capacities. The American Society for Testing and Materials D790 (7), was chosen for mechanical characterization of the specimens. This approach provided a quantifiable means of comparing each recipe by determining the modulus of elasticity from the load-deflection curves for each sample. These baseline data, in conjunction with the ballistic data, provided a reasonable first-level recipe selection process.

The 0.25-inch-thick panels were machined to 1-inch x 10-inch (WxL) flexural specimens with a Flow International Corporation waterjet system. Cutting such a flexible material proved to be a challenge. The material was machinable, but the edges tended to curl or bevel from the cutting process. Various cutting techniques and a stiffening material added during the cutting process were evaluated. The waterjet cutter, with particle board on the bottom surface of the sample, showed the best results. This method worked well but did not totally eliminate the problem. Therefore, all samples were re-pressed after machining at room temperature (~70 °F) and 500 psi for 0.5 hour. This added pressing step was performed after samples were dried at room temperature for about a week.

Four-point bend tests were performed on an Instron Electromechanical Testing System (Model 4405) with Series IX Material Testing Software. Samples were conditioned according to the standard before testing. A minimum of five samples was tested for each candidate recipe. Samples with thermoset prepregs on one side were tested with the thermoset side facing down, in tension. This would be a true representation of how the helmet would be molded with the stiff material on the outside to accommodate the flexural stresses induced during attempts to collapse the shell in compression.

⁸Teflon is a registered trademark of E. I. DuPont de Nemours & Co., Inc.

5. Helmet Manufacturing Considerations

Fully realizing the material and performance benefits of thermoplastic-aramids and hybridized solutions will require rethinking of the manufacturing processes currently in use by most of the U.S. helmet manufacturers. Current processes are configured for mass production of thermoset-based, monolithic Kevlar helmets. These manufacturing systems typically use expensive, matched steel tools to consolidate the materials. Cold helmet pre-forms are placed in a hot mold and held under pressure until fully cured. The tools are heated at 325 °F to promote the cross-linking of the phenolic resin. “Bump” and “burp” cycles are used to draw off undesirable gases that evolve during the cure. By contrast, thermoplastic manufacturing cycles have a number of attractive features. Secondary innovations could be introduced in the optimization of a pre-form design and cutting with the use of software and near-net patterns. Table 1 summarizes the essential difference of the two material and process-based approaches.

Table 1. Comparison of current and proposed helmet manufacturing methods.

| | Current Approach | Future Approach |
|----------------|--------------------------|---------------------------|
| Tool type | Matched metal (costly) | Female with silicone plug |
| Heat source | Conduction (heated tool) | Infrared |
| Pressure | Hydraulic press | Hydraulic press |
| Resin type | Thermoset | Thermoplastic |
| Fiber type | Monolithic | Hybrid |
| Cycle time | 15 minutes | 5 minutes |
| Pre-form scrap | 15 to 20% | 5 to 10% |

Ideally, a new process should be conceived that would simultaneously address the materials and fabrication deficiencies of current manufacturing methods and fully exploit the inherent benefits of thermoplastic-based processes. Figure 7 is a conceptual schematic of such a process. Material waste could be reduced or eliminated if neat pre-forms are developed and the reinforcement is hybridized. Infrared heating would rapidly heat the thermoplastic matrix and a silicone plug could be used to improve the hydrostatic pressure distribution used to consolidate the final shell.

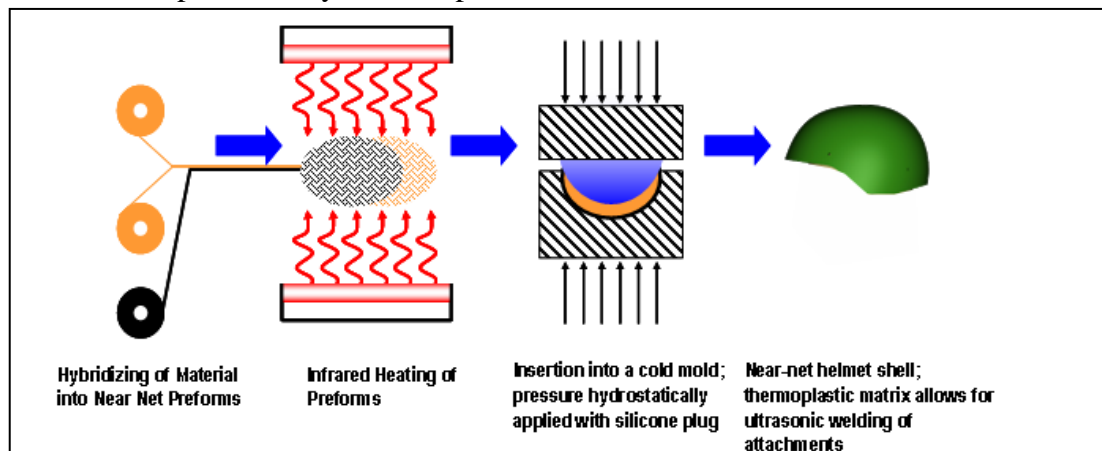


Figure 7. An integrated, low scrap and low cost semi-automated hybrid helmet process.

5.1 Series Fabrication

A logical approach in fabricating a structure made of two or more materials is to assign a processing step for each material system. For example, the thermoplastic matrix-based aramid could be placed in the helmet mold and processed under a minimum of 3500 kPa and a temperature of at least 120° Celsius. Once the helmet is formed, cooled, and stabilized, a secondary process step could be employed, which would apply a layer of graphite to the aramid-thermoplastic “core.” This could be done with a vacuum curable prepreg, provided the cured and finished laminate demonstrates the required stiffening effects for the overall helmet system. This process approach can be considered a series-type manufacturing method insofar as the material systems are separately and sequentially fabricated. A schematic of a basic series process cycle is shown in figure 8a. The advantage of this method is that, given two distinct resin types (thermoplastic and thermoset), having two separate process steps ensures an optimal process cycle for each material. The disadvantage is that this process method inherently introduces a secondary process step, and as such could increase process cycle time, touch labor, and secondary process infrastructure.

5.2 Parallel Fabrication

A possible remedy for minimizing or eliminating additional process steps in the manufacture of hybridized material systems is to combine the material assembly as much as possible and co-process the materials together. Generally, the aramid fibers are tolerant to relatively mild variances in process temperatures. The matrix materials, however, are not; indeed, thermoplastic matrices typically process at temperatures below thermosets. However, it is possible to select thermoset resin systems that are curable at or near the temperatures required to melt and consolidate the thermoplastic matrix material. Prudently selecting the matrix material provides the opportunity to effectively co-process the materials. Figure 8b schematically depicts this parallel process approach. The advantages of this manufacturing method are the ability to reduce the number of overall processing steps and to minimize the labor and cycle time required to effectively produce a hybridized helmet material system (8). The disadvantage is the possible limitation of certain thermoset resin systems if the cure temperature far exceeds the process cycle temperature for melting and consolidating the thermoplastic. The time required for curing the thermoset skin will influence the total process cycle time.

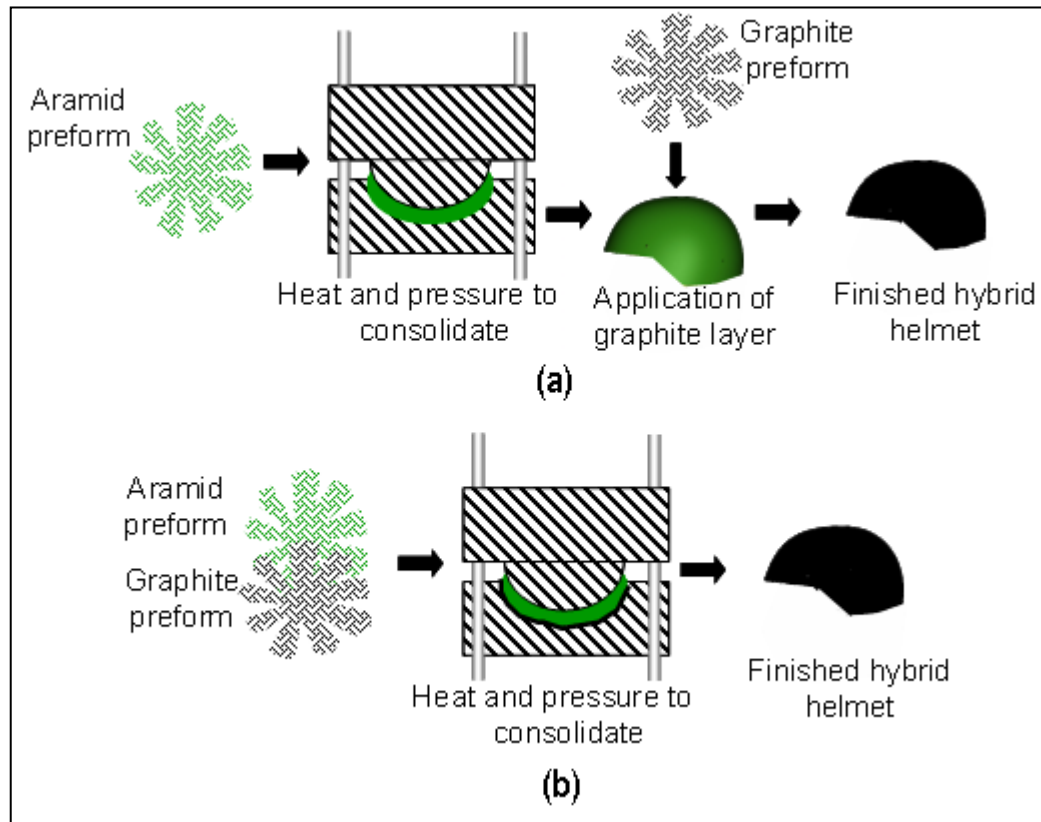


Figure 8. A comparison of series and parallel fabrication cycles for hybrid helmet manufacture.

6. Results and Discussion

ARL has explored a variety of thermoplastic-based systems, including hybridized derivatives. The flexural data for both thermoplastic Kevlar KM2 and IM7-epoxy thermoplastic KM2 hybrid are shown in figure 9. Table 2 provides a summary of flexural modulus data for some of the ballistic recipes that were explored. The preliminary conclusions based on ballistic and mechanical data are that it is possible to reduce the overall areal density of a typical PASGT shell (Kevlar 29-phenolic) by 25% with the use of hybridized, thermoplastic based aramids. It appears that the dominating design factors at reduced weight are static and dynamic structural rigidity and integrity. Simply preventing penetration of a bullet or high speed fragment is not a sufficient condition for Soldier-borne head protection. The deformations witnessed with monolithic thermoplastic aramid systems rapidly increase, raising serious concerns about localized and blunt force trauma such as fracturing of the skull. Still, through hybridization and prudent design trade-offs, it is possible to construct a thermoplastic based helmet with superior mass-efficient ballistic properties as compared to current thermoset helmet shell systems.

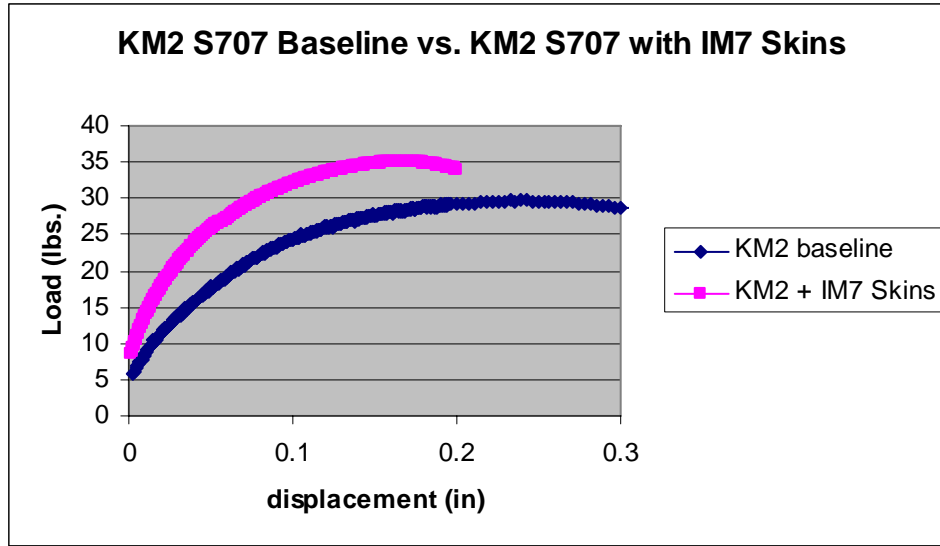


Figure 9. A comparison of monolithic and hybrid (IM7 graphite) thermoplastic KM2.

Table 2. Mechanical data for monolithic and hybrid recipes.

| | | | | | |
|---------|---------------------------------------|------|--------|--------|-----------|
| TP0721G | 30 plies S707 + 2 plies S2/M36 | Comp | 0.2574 | 0.0009 | 2,808,121 |
| TP077C | 40 plies S707 + 2 plies S2 FgBT250E | Tens | 0.2602 | 0.0015 | 2,334,024 |
| TP077C | 40 plies S707 + 2 plies S2 FgBT250E | Comp | 0.2615 | 0.0004 | 2,587,133 |
| TP05c1 | 32 plies 705/SP | N/A | 0.2693 | 0.0006 | 2,403,230 |
| TP0710D | 41 plies S707 + 2 plies K49 Bt250E | Tens | 0.2668 | 0.001 | 2,414,482 |
| TP0710D | 41 plies S707 + 2 plies K49 Bt250E | Comp | 0.2672 | 0.0004 | 2,782,257 |
| TP0733K | 41 plies S707 + 1 ply Twintex EG/PP | Tens | 0.276 | 0.001 | 1,778,301 |
| TP0733K | 41 plies S707 + 1 ply Twintex EG/PP | Comp | 0.2747 | 0.0016 | 1,906,098 |
| TP05b3 | 31 plies 705/PU | N/A | 0.2836 | 0.0009 | 193,221 |
| TP0730J | 42 plies S707 + 1 ply Twintex C/N | Tens | 0.2826 | 0.0011 | 1,245,251 |
| TP0730J | 42 plies S707 + 1 ply Twintex C/N | Comp | 0.2836 | 0.0012 | 1,217,542 |
| TP075A | 42 plies S707 + 2 plies Cytec 381/IM7 | Tens | 0.2673 | 0.0004 | 2,741,839 |
| TP075A | 42 plies S707 + 2 plies Cytec 381/IM7 | Comp | 0.2674 | 0.0011 | 3,126,790 |
| TEPNY | TEP/NYLON | N/A | 0.2831 | | 903,264 |
| TP0740A | Double-Sided S707/TP | N/A | 0.2644 | | 4,111,269 |
| TP0741N | S707/TP/Kevlar/Phenolic/PVB | Tens | 0.2662 | | 1,784,187 |
| TP0741N | S707/TP/Kevlar/Phenolic/PVB | Comp | 0.2661 | | 1,751,947 |

The development of the materials and processes in this research is pertinent not only to next-generation helmet systems but to currently fielded systems as well. For example, as shown in

figure 10, as each new and improved thermoplastic recipe is developed, it is possible to consider one of two uses for this technology. The first is a lighter helmet shell that delivers essentially the same ballistic, static, and dynamic characteristics as a current helmet (e.g., the PASGT). This is the current intention of the FFW. However, a second option is to consider providing an improved level of protection at the same weight. For example, this could entail replacing the Kevlar 29-phenolic with KM2-thermoplastic hybridized with a stiffening material (e.g., glass or graphite). This helmet could exhibit less deformation and improved ballistics at the same weight of the current PASGT system.

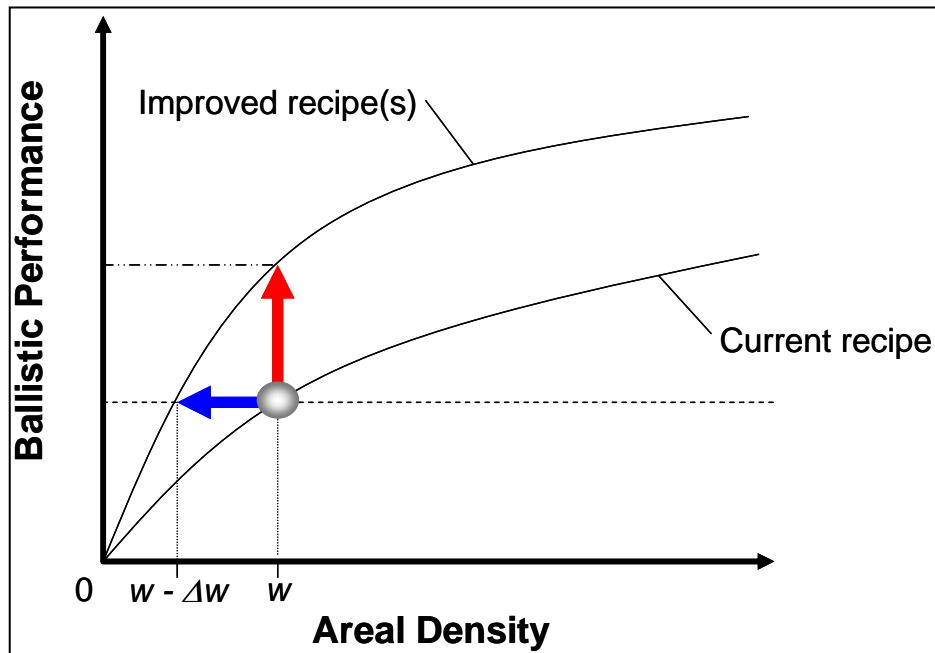


Figure 10. Applicability of new helmet recipes to current and future helmet systems.

6.1 Flat Plate Fabrication and Results

Previous studies had initiated the fabrication of flat plate specimens for structural and ballistic testing (5). Each of the flat plate “recipes” represented a potential helmet material solution to meet key performance requirements that included fragmentation, dynamic deflection, and structural integrity. The current research focused on refining the leading candidate recipe, which consists of IM7 graphite-epoxy co-processed with a polyolefin matrix, Kevlar KM2 woven reinforcement (figure 11). It is possible to reduce the weight and increase protection levels simultaneously (table 3).

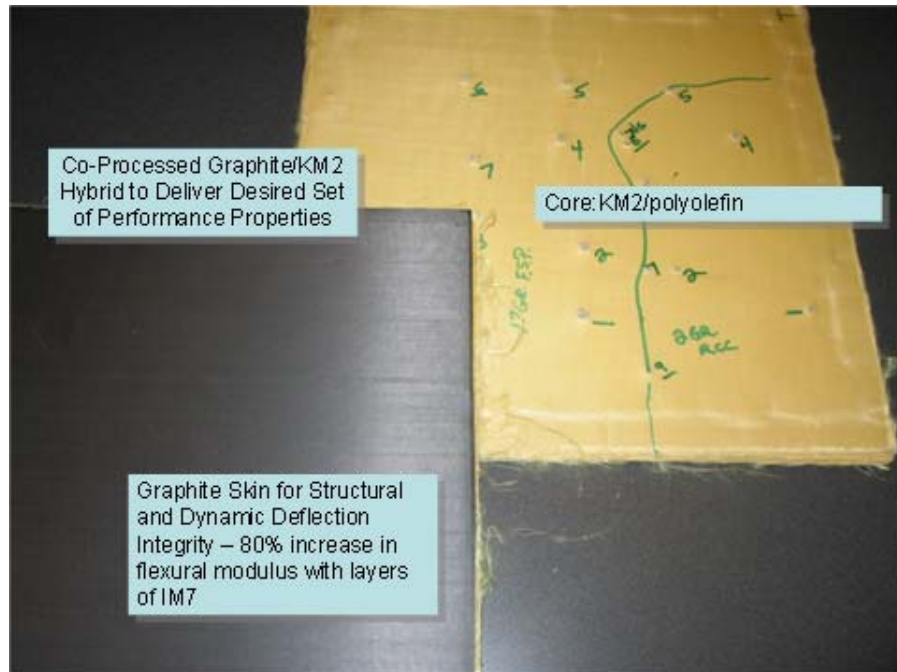


Figure 11. ARL recipe.

Table 3. A comparison of PASGT and hybrid shell materials.

| All data normalized using PASGT as baseline | PASGT | KM2-polyolefin Hybrid |
|---|-------|-----------------------|
| Normalized Areal Density | 1 | 0.76 |
| Normalized 2-grain V_{50} | 1 | 1.02 |
| Normalized 17 grain V_{50} | 1 | 1.20 |

6.2 Helmet Design Variations

Once a viable hybridized material recipe was identified (in this case, a graphite-KM2 polyolefin), it was possible to use the aforementioned processes to begin forming the materials into a helmet shell. The goal was twofold: to characterize the influence of the process cycle on the material and to explore weight-saving methods of selectively stiffening the helmet shell. Helmet fabrication was performed by Diaphorm LLC (Limited Liability Company) in accordance with ARL materials, designs, and process specifications.

6.2.1 Monolithic KM2 Shell-Polyolefin Shell

It is important to have a baseline when one is developing a hybridized material system. In this particular application, the base material is polyolefin-KM2 (aramid) composite. Figure 12 shows the results of consolidating this material into a helmet shell. For these studies, the helmet shell “shape” is arbitrary as long as it remains fixed for each of the subsequent material variations. “Petal” shapes are apparent on the aramid fabric in order to limit wrinkling during molding. Since there is no thermoset present, the polyolefin melts, conforms fully to the mold shape, and

upon cooling, retains the shape and rigidity associated with the mold and KM2-thermoplastic material.

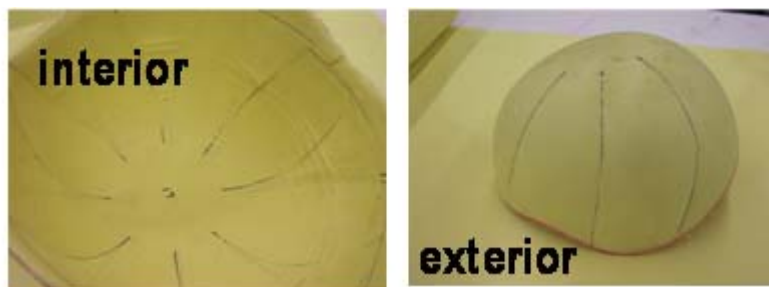


Figure 12. Monolithic shell composed of KM2-polyolefin.

6.2.2 Graphite Skin on Polyolefin-KM2 Shell

The first variation is the application of a graphite-epoxy skin to the outer surface of the KM2-polyolefin, as shown in figure 13. Some of the latter material was removed to keep the areal density of the helmet consistent with the monolithic KM2-polyolefin shell. Like the flat plate work that preceded it, the bond between the graphite-epoxy and the KM2-polyolefin was excellent. Because a silicone plug, instead of the matched compression tooling, was used to consolidate, some wrinkling on the interior of the shell was apparent.

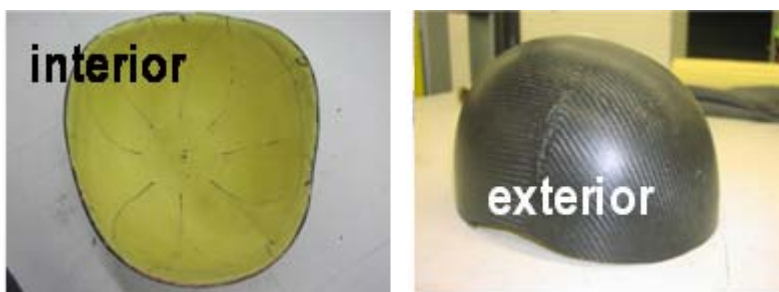


Figure 13. Graphite-epoxy on outer surface of KM2-polyolefin shell.

6.2.3 Polyolefin-KM2 Encapsulated by Thermoplastic Graphite

A second variation was the application of a graphite-nylon layer to the interior and exterior surfaces of the KM2-polyolefin shell, as shown in figure 14. Again, the areal density was kept equivalent to the monolithic KM2-polyolefin shell. This shell was extremely stiff even though the nylon thermoplastic modulus was less than that of the graphite-epoxy material. This variation also demonstrates the total elimination of thermoset matrices in the stiffening or ballistic components of the helmet. Cure kinetics were not an issue in determining the cycle time for this process. Only the ballistic capability of the skin material is yet to be determined. Similarly, additional studies of the lower pressure consolidation influence on ballistics are required.

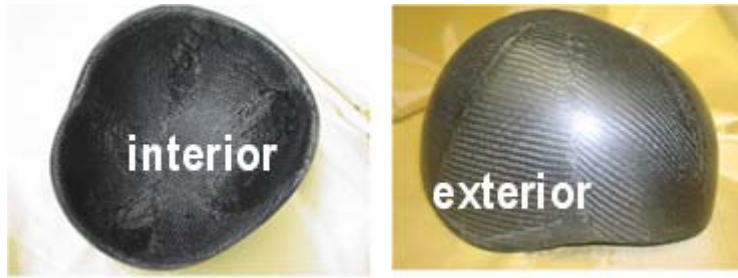


Figure 14. KM2-polyolefin fully encapsulated by graphite-nylon.

6.2.4 Integrally Stiffened Polyolefin-KM2 Shell

A third variation is the *selective* application of a graphite-epoxy material to the KM2-polyolefin ballistic “core.” Like the first variation, two layers of graphite-epoxy were applied to the exterior surface of the KM2-polyolefin shell as shown in figure 15. However, graphite was applied in a hoop on the lower perimeter of the shell, as well as in a U-shaped piece in the middle interior of the shell. The purpose was to selectively stiffen only those regions that required it, thereby minimizing weight. A limited amount of wrinkling is apparent on the inner surface, which is attributable to low pressure consolidation.



Figure 15. Integrally stiffened KM2-polyolefin shell.

7. Conclusions

A series of thermoplastic-based aramid materials has been hybridized with secondary structural materials. These specimens have been characterized ballistically and structurally. The conclusion is that thermoplastic based systems can yield a 10 to 25% weight reduction over conventional thermoset (PVB phenolic) helmet materials while maintaining equivalent protection levels. The focus of the present work is to begin identifying materials and design opportunities that could be used to engineer a lighter helmet that meets prescribed baseline performance specifications. In addition, practical manufacturing methods for producing these systems have been identified and preliminary prototypes of these new material and system designs have been fabricated through relatively low pressure manufacturing.

8. References

1. McManus, L. R.; Durand, P. E.; Claus, W. D., *Development of a One Piece Infantry Helmet*; 76-30-CEMEL; U.S. Army Natick Research and Development Command Report, 1976.
2. Riewald, P. G.; Folgar, F.; Yang, H. H.; Shaughnessy, W. F. Lightweight Helmet from a New Aramid Fiber. *Proc. 23rd SAMPE Tech. Conf.*, NY, 1991.
3. Effing, M.; Hopkins, M. W.; Beyeler, E. P. The Tepex System: Cost Effective High Volume Production of Parts and Profiles for Recreation, Protection and Transportation Markets. *Proc. 38th Int. SAMPE Symp. and Exhibition*, 1994.
4. Yang, H. H. *Kevlar Aramid Fiber*; John Wiley & Sons, NY, 1993.
5. Cunniff, P. M.; Auerbach, M. A.; Vetter, E.; Sikkema, D.J. High Performance “M5” Fiber for Ballistics/Structural Composites. *Proc. Int. Ballistics Symp*, 2002.
6. Van der Jagt; Beukers, A. The Potential for a New Rigid-Rod Polymer Fibre (‘M5’) in Advanced Composite Structures. *Polymer* **1999**, 40, 1035-1044.
7. American Society for Testing and Materials D790, 1990 Annual Book of ASTM Standards, Section 8, Plastics, V 08,01, Plastics (1): C177-D1660, 1990.
8. Walsh, S. M.; Spagnuolo, D.; Scott, B. The Potential Advantages of Thermoplastic and Hybridized Ballistic Materials and Processes on U.S. Army Helmet Development, *Proceedings of the Society for the Advancement of Materials and Process Engineering*, May 3, 2004, Long Beach, CA.

| NO. OF COPIES | ORGANIZATION |
|--------------------|--|
| 1 (PDF ONLY) | DEFENSE TECHNICAL INFORMATION CTR DTIC OCA 8725 JOHN J KINGMAN RD STE 0944 FORT BELVOIR VA 22060-6218 |
| 1 | US ARMY RSRCH DEV & ENGRG CMD SYSTEMS OF SYSTEMS INTEGRATION AMSRD SS T 6000 6TH ST STE 100 FORT BELVOIR VA 22060-5608 |
| 1 | INST FOR ADVNCD TCHNLGY THE UNIV OF TEXAS AT AUSTIN 3925 W BRAKER LN STE 400 AUSTIN TX 78759-5316 |
| 1 | DIRECTOR US ARMY RESEARCH LAB IMNE ALC IMS 2800 POWDER MILL RD ADELPHI MD 20783-1197 |
| 1 | DIRECTOR US ARMY RESEARCH LAB AMSRD ARL CI OK TL 2800 POWDER MILL RD ADELPHI MD 20783-1197 |
| 2 | DIRECTOR US ARMY RESEARCH LAB AMSRD ARL CS OK T 2800 POWDER MILL RD ADELPHI MD 20783-1197 |
| 1 | DIRECTOR US ARMY RESEARCH LAB ATTN AMSRD ARL SE DE R ATKINSON 2800 POWDER MILL RD ADELPHI MD 20783-1197 |
| 6 | DIR US ARMY RESEARCH LAB ATTN AMSRD ARL WM MB T LI A ABRAHAMIAN M BERMAN M CHOWDHURY A FRYDMAN E SZYMANSKI 2800 POWDER MILL RD ADELPHI MD 20783-1197 |

| NO. OF COPIES | ORGANIZATION |
|------------------|--|
| 1 | US ARMY RSRCH DEV & ENG CMD SYSTEMS OF SYSTEMS INTEGRATION ATTN AMSRD SS T 6000 6TH ST STE 100 FORT BELVOIR VA 22060-5608 |
| 1 | COMMANDER US ARMY MATERIEL CMD ATTN AMXMI INT 5001 EISENHOWER AVE ALEXANDRIA VA 22333-0001 |
| 3 | PM MAS ATTN SFAE AMO MAS SFAE AMO MAS MC CHIEF ENGINEER PICATINNY ARSENAL NJ 07806-5000 |
| 2 | PM MAS ATTN SFAE AMO MAS PS SFAE AMO MAS LC PICATINNY ARSENAL NJ 07806-5000 |
| 1 | CDR US ARMY ARDEC ATTN AMSTA AR CC COL JENKER PICATINNY ARSENAL NJ 07806-5000 |
| 1 | CDR US ARMY ARDEC ATTN AMSTA AR FSE PICATINNY ARSENAL NJ 07806-5000 |
| 1 | CDR US ARMY ARDEC ATTN AMSTA AR TD PICATINNY ARSENAL NJ 07806-5000 |
| 7 | CDR US ARMY ARDEC ATTN AMSTA AR CCH A D VO F ALTAMURA M NICOLICH M PALATHINGUL R HOWELL A VELLA M YOUNG PICATINNY ARSENAL NJ 07806-5000 |
| 6 | CDR US ARMY ARDEC ATTN AMSTA AR CCH A L MANOLE S MUSALLI R CARR M LUCIANO E LOGSDEN T LOUZEIRO PICATINNY ARSENAL NJ 07806-5000 |

NO. OF
COPIES ORGANIZATION

1 CDR US ARMY ARDEC
ATTN AMSTA AR CCH P J LUTZ
PICATINNY ARSENAL NJ 07806-5000

1 CDR US ARMY ARDEC
ATTN AMSTA AR FSF T C LIVECCHIA
PICATINNY ARSENAL NJ 07806-5000

1 CDR US ARMY ARDEC
ATTN AMSTA ASF
PICATINNY ARSENAL NJ 07806-5000

1 CDR US ARMY ARDEC
ATTN AMSTA AR QAC T C J PAGE
PICATINNY ARSENAL NJ 07806-5000

1 CDR US ARMY ARDEC
ATTN AMSTA AR M D DEMELLA
PICATINNY ARSENAL NJ 07806-5000

3 CDR US ARMY ARDEC
ATTN AMSTA AR FSA A WARNASH
B MACHAK M CHIEFA
PICATINNY ARSENAL NJ 07806-5000

2 CDR US ARMY ARDEC
ATTN AMSTA AR FSP G M SCHIKSNIS
D CARLUCCI
PICATINNY ARSENAL NJ 07806-5000

2 CDR US ARMY ARDEC
ATTN AMSTA AR CCH C H CHANIN
S CHICO
PICATINNY ARSENAL NJ 07806-5000

1 CDR US ARMY ARDEC
ATTN AMSTA AR QAC T D RIGOGLIOSO
PICATINNY ARSENAL NJ 07806-5000

1 CDR US ARMY ARDEC
ATTN AMSTA AR WEL F M GUERRIERE
PICATINNY ARSENAL NJ 07806-5000

9 CDR US ARMY ARDEC
ATTN AMSTA AR CCH B P DONADIA
F DONLON P VALENTI
C KNUTSON G EUSTICE
K HENRY J MCNABOC
R SAYER F CHANG
PICATINNY ARSENAL NJ 07806-5000

1 PM ARMS
ATTN SFAE GCSS ARMS
BLDG 171
PICATINNY ARSENAL NJ 07806-5000

NO. OF
COPIES ORGANIZATION

1 CDR US ARMY ARDEC
ATTN AMSTA AR WEA J BRESCIA
PICATINNY ARSENAL NJ 07806-5000

1 CDR US ARMY TACOM
PM COMBAT SYSTEMS
ATTN SFAE GCS CS
6501 ELEVEN MILE RD
WARREN MI 48397-5000

1 CDR US ARMY TACOM
PM SURVIVABLE SYSTEMS
ATTN SFAE GCSS W GSI H M RYZYI
6501 ELEVEN MILE RD
WARREN MI 48397-5000

1 CDR US ARMY TACOM
CHIEF ABRAMS TESTING
ATTN SFAE GCSS W AB QT
T KRASKIEWICZ
6501 ELEVEN MILE RD
WARREN MI 48397-5000

1 COMMANDER
US ARMY TACOM
ATTN AMSTA SF
WARREN MI 48397-5000

1 DIR AIR FORCE RSCH LAB
ATTN MLLMD D MIRACLE
2230 TENTH ST
WRIGHT PATTERSON AFB OH 45433-7817

1 OFC OF NAVAL RESEARCH
ATTN J CHRISTODOULOU
ONR CODE 332
800 N QUINCY ST
ARLINGTON VA 22217-5600

1 CDR WATERVLIET ARSENAL
ATTN SMCWV QAE Q B VANINA
BLDG 44
WATERVLIET NY 12189-4050

2 HQ IOC TANK
AMMUNITION TEAM
ATTN AMSIO SMT R CRAWFORD
W HARRIS
ROCK ISLAND IL 61299-6000

2 COMMANDER
US ARMY AMCOM
AVIATION APPLIED TECH DIR
ATTN J SCHUCK
FORT EUSTIS VA 23604-5577

NO. OF
COPIES ORGANIZATION

1 NSWC
DAHLGREN DIV CODE G06
DAHLGREN VA 22448

2 US ARMY CORPS OF ENGINEERS
ATTN CERD C T LIU
CEW ET T TAN
20 MASSACHUSETTS AVE NW
WASHINGTON DC 20314

1 US ARMY COLD REGIONS
RSCH & ENGRNG LAB
ATTN P DUTTA
72 LYME RD
HANOVER NH 03755

4 CDR US ARMY TACOM
ATTN AMSTA TR R MCCLELLAND
D THOMAS J BENNETT
D HANSEN
WARREN MI 48397-5000

4 CDR US ARMY TACOM
ATTN AMSTA JSK S GOODMAN
J FLORENCE D TEMPLETON
A SCHUMACHER
WARREN MI 48397-5000

5 CDR US ARMY TACOM
ATTN AMSTA TR D D OSTBERG
L HINOJOSA B RAJU
AMSTA CS SF H HUTCHINSON
F SCHWARZ
WARREN MI 48397-5000

6 BENET LABS
ATTN AMSTA AR CCB R FISCELLA
M SOJA E KATHE G FRIAR
M SCAVULO G SPENCER
WATERVLIET NY 12189-4050

4 BENET LABS
ATTN AMSTA AR CCB P WHEELER
S KRUPSKI J VASILAKIS
R HASENBEIN
WATERVLIET NY 12189-4050

4 BENET LABS
ATTN AMSTA CCB R S SOPOK
E HYLAND D CRAYON
R DILLON
WATERVLIET NY 12189-4050

NO. OF
COPIES ORGANIZATION

1 USA SBCCOM PM SOLDIER SPT
ATTN AMSSB PM RSS A J CONNORS
KANSAS ST
NATICK MA 01760-5057

1 NSWC
TECH LIBRARY CODE B60
17320 DAHLGREN RD
DAHLGREN VA 22448

2 USA SBCCOM
MATERIAL SCIENCE TEAM
ATTN AMSSB RSS J HERBERT
M SENNETT
KANSAS ST
NATICK MA 01760-5057

2 OFC OF NAVAL RESEARCH
ATTN D SIEGEL CODE 351 J KELLY
800 N QUINCY ST
ARLINGTON VA 22217-5660

1 NSWC
CRANE DIVISION
M JOHNSON CODE 20H4
LOUISVILLE KY 40214-5245

2 NSWC
ATTN U SORATHIA
C WILLIAMS CODE 6551
9500 MACARTHUR BLVD
WEST BETHESDA MD 20817

2 CDR NSWC
CARDEROCK DIVISION
ATTN R PETERSON CODE 2020
M CRITCHFIELD CODE 1730
BETHESDA MD 20084

4 DIR US ARMY NGIC
ATTN D LEITER MS 404
J GASTON MS 301
M HOLTUS MS 301
M WOLFE MS 307
2055 BOULDERS RD
CHARLOTTESVILLE VA 22911-8318

4 DIR US ARMY NGIC
ATTN S MINGLEDORF MS 504
W GSTATTENBAUER MS 304
R WARNER MS 305
J CRIDER MS 306
2055 BOULDERS RD
CHARLOTTESVILLE VA 22911-8318

| <u>NO. OF COPIES</u> | <u>ORGANIZATION</u> |
|--------------------------|---|
| 1 | NAVAL SEA SYSTEMS CMD ATTN D LIESE 1333 ISAAC HULL AVE SE 1100 WASHINGTON DC 20376-1100 |
| 4 | US ARMY SBCCOM SOLDIER SYSTEMS CTR BALLISTICS TEAM ATTN J WARD W ZUKAS P CUNNIFF J SONG KANSAS ST NATICK MA 01760-5019 |
| 3 | US ARMY SBCCOM SOLDIER SYSTEMS CTR MARINE CORPS TEAM J MACKIEWICZ ATTN AMSSB RCP SS W NYKVIST S BEAUDOIN KANSAS ST NATICK MA 01760-5019 |
| 7 | US ARMY RESEARCH OFC ATTN A CROWSON H EVERITT J PRATER G ANDERSON D STEPP D KISEROW J CHANG PO BOX 12211 RSCH TRIANGLE PARK NC 27709-2211 |
| 1 | AFRL MLBC 2941 P ST RM 136 WRIGHT PATTERSON AFB OH 45433-7750 |
| 1 | DIRECTOR LOS ALAMOS NATL LAB ATTN F L ADDESSIO T 3 MS 5000 PO BOX 1633 LOS ALAMOS NM 87545 |
| 4 | NSWC ATTN J FRANCIS CODE G30 D WILSON CODE G32 R D COOPER CODE G32 J FRAYSSE CODE G33 DAHLGREN VA 22448 |
| 4 | NSWC ATTN T DURAN CODE G33 L DE SIMONE CODE G33 R HUBBARD CODE G33 DAHLGREN VA 22448 |

| <u>NO. OF COPIES</u> | <u>ORGANIZATION</u> |
|--------------------------|--|
| 1 | NSWC CARDEROCK DIVISION R CRANE CODE 6553 9500 MACARTHUR BLVD WEST BETHESDA MD 20817-5700 |
| 1 | AFRL MLSS ATTN R THOMSON 2179 12TH ST RM 122 WRIGHT PATTERSON AFB OH 45433-7718 |
| 2 | AFRL ATTN F ABRAMS J BROWN BLDG 653 2977 P ST STE 6 WRIGHT PATTERSON AFB OH 45433-7739 |
| 5 | DIR LAWRENCE LIVERMORE NATL LAB ATTN R CHRISTENSEN S DETERESA F MAGNESS M FINGER MS 313 M MURPHY L 282 PO BOX 808 LIVERMORE CA 94550 |
| 1 | AFRL MLS OL ATTN L COULTER 5851 F AVE BLDG 849 RM AD1A HILL AFB UT 84056-5713 |
| 1 | OSD JOINT CCD TEST FORCE ATTN OSD JCCD R WILLIAMS 3909 HALLS FERRY RD VICKSBURG MS 29180-6199 |
| 3 | DARPA ATTN M VANFOSSEN S WAX L CHRISTODOULOU 3701 N FAIRFAX DR ARLINGTON VA 22203-1714 |
| 3 | OAK RIDGE NATL LAB ATTN R M DAVIS C EBERLE MS 8048 C D WARREN MS 8039 PO BOX 2008 OAK RIDGE TN 37831-6195 |

| <u>NO. OF</u> <u>COPIES</u> | <u>ORGANIZATION</u> | <u>NO. OF</u> <u>COPIES</u> | <u>ORGANIZATION</u> |
|--------------------------------|---|--------------------------------|--|
| 3 | DIR SANDIA NATL LABS APPLIED MECHS DEPT ATTN MS 9042 J HANDROCK Y R KAN J LAUFFER PO BOX 969 LIVERMORE CA 94551-0969 | 1 | DIR DEFENSE INTLGNC AGENCY TA 5 ATTN K CRELLING WASHINGTON DC 20310 |
| 4 | NIST ATTN M VANLANDINGHAM MS 8621 J CHIN MS 8621 J MARTIN MS 8621 D DUTHINH MS 8611 100 BUREAU DR GAITHERSBURG MD 20899 | 1 | COMPOSITE MATERIALS INC ATTN D SHORTT 19105 63 AVE NE PO BOX 25 ARLINGTON WA 98223 |
| 1 | HYDROGEOLOGIC INC ATTN SERDP ESTCP SPT OFC S WALSH 1155 HERNDON PKWY STE 900 HERNDON VA 20170 | 1 | JPS GLASS ATTN L CARTER PO BOX 260 SLATER RD SLATER SC 29683 |
| 3 | NASA LANGLEY RSCH CAR ATTN AMSRD ARL VT W ELBER MS 266 F BARTLETT JR MS 266 G FARLEY MS 266 HAMPTON VA 23681-0001 | 1 | COMPOSITE MATERIALS INC ATTN R HOLLAND 11 JEWEL CT ORINDA CA 94563 |
| 1 | FWHA ATTN E MUNLEY 6300 GEORGETOWN PIKE MCLEAN VA 22101 | 1 | COMPOSITE MATERIALS INC ATTN C RILEY 14530 S ANSON AVE SANTA FE SPRINGS CA 90670 |
| 1 | USDOT FEDERAL RAILROAD ATTN M FATEH RDV 31 WASHINGTON DC 20590 | 1 | SIMULA ATTN R HUYETT 10016 S 51ST ST PHOENIX AZ 85044 |
| 3 | CYTEC FIBERITE ATTN R DUNNE D KOHLI R MAYHEW 1300 REVOLUTION ST HAVRE DE GRACE MD 21078 | 2 | PROTECTION MATERIALS INC ATTN M MILLER F CRILLEY 14000 NW 58 CT MIAMI LAKES FL 33014 |
| 1 | DIR NGIC ATTN IANG TMT 2055 BOULDERS RD CHARLOTTESVILLE VA 22911-8318 | 2 | FOSTER MILLER ATTN M ROYLANCE W ZUKAS 195 BEAR HILL RD WALTHAM MA 02354-1196 |
| 2 | 3TEX CORP ATTN A BOGDANOVICH J SINGLETARY 109 MACKENAN DR CARY NC 27511 | 1 | ROM DEVELOPMENT CORP ATTN R O MEARA 136 SWINEBURNE ROW BRICK MARKET PLACE NEWPORT RI 02840 |
| | | 2 | TEXTRON SYSTEMS ATTN M TREASURE T FOLTZ 1449 MIDDLESEX ST LOWELL MA 01851 |

| <u>NO. OF COPIES</u> | <u>ORGANIZATION</u> |
|--------------------------|---|
| 1 | O GARA HESS & EISENHARDT ATTN M GILLESPIE 9113 LESAIN DR FAIRFIELD OH 45014 |
| 1 | MILLIKEN RESEARCH CORP ATTN M MACLEOD PO BOX 1926 SPARTANBURG SC 29303 |
| 1 | CONNEAUGHT INDUSTRIES INC ATTN J SANTOS PO BOX 1425 COVENTRY RI 02816 |
| 1 | ARMTEC DEFENSE PRODUCTS ATTN S DYER 85 901 AVE 53 PO BOX 848 COACHELLA CA 92236 |
| 3 | PACIFIC NORTHWEST LAB ATTN M SMITH G VAN ARSDALE R SHIPPELL PO BOX 999 RICHLAND WA 99352 |
| 1 | ALLIANT TECHSYSTEMS INC 4700 NATHAN LN N PLYMOUTH MN 55442-2512 |
| 1 | APPLIED COMPOSITES ATTN W GRISCH 333 NORTH SIXTH ST ST CHARLES IL 60174 |
| 1 | CUSTOM ANALYTICAL ENG SYS INC ATTN A ALEXANDER 13000 TENSOR LANE NE FLINTSTONE MD 21530 |
| 1 | AAI CORP ATTN DR N B MCNELLIS PO BOX 126 HUNT VALLEY MD 21030-0126 |
| 1 | OFC DEPUTY UNDER SEC DEFNS ATTN J THOMPSON 1745 JEFFERSON DAVIS HWY CRYSTAL SQ 4 STE 501 ARLINGTON VA 22202 |

| <u>NO. OF COPIES</u> | <u>ORGANIZATION</u> |
|--------------------------|--|
| 3 | ALLIANT TECHSYSTEMS INC ATTN J CONDON E LYNAM J GERHARD WV01 16 STATE RT 956 PO BOX 210 ROCKET CENTER WV 26726-0210 |
| 1 | PROJECTILE TECHNOLOGY INC 515 GILES ST HAVRE DE GRACE MD 21078 |
| 1 | PRATT & WHITNEY ATTN C WATSON 400 MAIN ST MS 114 37 EAST HARTFORD CT 06108 |
| 5 | NORTHROP GRUMMAN ATTN B IRWIN K EVANS D EWART J MCGLYNN A SHREKENHAMER BLDG 160 DEPT 3700 1100 W HOLLYVALE ST AZUSA CA 91701 |
| 1 | BRIGS COMPANY ATTN J BACKOFEN 2668 PETERBOROUGH ST HERNDON VA 22071-2443 |
| 1 | ZERNOW TECHNICAL SERVICES ATTN L ZERNOW 425 W BONITA AVE STE 208 SAN DIMAS CA 91773 |
| 2 | GENERAL DYNAMICS OTS FLINCHBAUGH DIV ATTN K LINDE T LYNCH PO BOX 127 RED LION PA 17356 |
| 1 | GKN WESTLAND AEROSPACE ATTN D OLDS 450 MURDOCK AVE MERIDEN CT 06450-8324 |
| 1 | BOEING ROTORCRAFT ATTN P HANDEL 800 B PUTNAM BLVD WALLINGFORD PA 19086 |

| <u>NO. OF COPIES</u> | <u>ORGANIZATION</u> |
|--------------------------|---|
| 5 | SIKORSKY AIRCRAFT ATTN G JACARUSO J ADELMANN T CARSTENSAN B KAY S GARBO MS S330A 6900 MAIN ST PO BOX 9729 STRATFORD CT 06497-9729 |
| 1 | AEROSPACE CORP ATTN G HAWKINS M4 945 2350 E EL SEGUNDO BLVD EL SEGUNDO CA 90245 |
| 2 | CYTEC FIBERITE ATTN M LIN W WEB 1440 N KRAEMER BLVD ANAHEIM CA 92806 |
| 2 | UDLP ATTN G THOMAS M MACLEAN PO BOX 58123 SANTA CLARA CA 95052 |
| 2 | UDLP ATTN R BRYNSVOLD P JANKE MS 170 4800 E RIVER RD MINNEAPOLIS MN 55421-1498 |
| 1 | LOCKHEED MARTIN SKUNK WORKS ATTN D FORTNEY 1011 LOCKHEED WAY PALMDALE CA 93599-2502 |
| 1 | NORTHROP GRUMMAN CORP ELECTRONIC SENSORS & SYSTEMS DIV ATTN E SCHOCH MS V 16 1745A W NURSERY RD LINTHICUM MD 21090 |
| 1 | GDLS DIVISION ATTN D BARTLE PO BOX 1901 WARREN MI 48090 |
| 2 | GDLS ATTN D REES M PASIK PO BOX 2074 WARREN MI 48090-2074 |

| <u>NO. OF COPIES</u> | <u>ORGANIZATION</u> |
|--------------------------|--|
| 1 | GDLS MUSKEGON OPER ATTN M SOIMAR 76 GETTY ST MUSKEGON MI 49442 |
| 1 | GENERAL DYNAMICS AMPHIBIOUS SYS SURVIVABILITY LEAD ATTN G WALKER 991 ANNAPOLIS WAY WOODBIDGE VA 22191 |
| 6 | INST FOR ADVANCED TECH ATTN H FAIR I MCNAB P SULLIVAN S BLESS W REINECKE C PERSAD 3925 W BRAKER LN STE 400 AUSTIN TX 78759-5316 |
| 1 | ARROW TECH ASSOC 1233 SHELBURNE RD STE D8 SOUTH BURLINGTON VT 05403-7700 |
| 1 | R EICHELBERGER CONSULTANT 409 W CATHERINE ST BEL AIR MD 21014-3613 |
| 1 | SAIC ATTN G CHRYSSOMALLIS 8500 NORMANDALE LAKE BLVD SUITE 1610 BLOOMINGTON MN 55437-3828 |
| 1 | UCLA MANE DEPT ENGR IV ATTN H T HAHN LOS ANGELES CA 90024-1597 |
| 1 | UMASS LOWELL PLASTICS DEPT ATTN N SCHOTT 1 UNIVERSITY AVE LOWELL MA 01854 |
| 1 | IIT RESEARCH CAR ATTN D ROSE 201 MILL ST ROME NY 13440-6916 |
| 1 | GA TECH RESEARCH INST GA INST OF TCHNLGY ATTN P FRIEDERICH ATLANTA GA 30392 |

| NO. OF COPIES | ORGANIZATION |
|------------------|--|
| 1 | MICHIGAN ST UNIV MSM DEPT ATTN R AVERILL 3515 EB EAST LANSING MI 48824-1226 |
| 1 | PENN STATE UNIV ATTN R S ENGEL 245 HAMMOND BLDG UNIVERSITY PARK PA 16801 |
| 1 | PENN STATE UNIV ATTN C BAKIS 212 EARTH ENGR SCIENCES BLDG UNIVERSITY PARK PA 16802 |
| 1 | PURDUE UNIV SCHOOL OF AERO & ASTRO ATTN C T SUN W LAFAYETTE IN 47907-1282 |
| 1 | UNIV OF MAINE ADV STR & COMP LAB ATTN R LOPEZ ANIDO 5793 AEWB BLDG ORONO ME 04469-5793 |
| 1 | JOHNS HOPKINS UNIV APPLIED PHYSICS LAB ATTN P WIENHOLD 11100 JOHNS HOPKINS RD LAUREL MD 20723-6099 |
| 1 | UNIV OF DAYTON ATTN J M WHITNEY COLLEGE PARK AVE DAYTON OH 45469-0240 |
| 5 | UNIV OF DELAWARE CTR FOR COMPOSITE MTRLs ATTN J GILLESPIE M SANTARE S YARLAGADDA S ADVANI D HEIDER 201 SPENCER LAB NEWARK DE 19716 |
| 1 | DEPT OF MTRLs SCIENCE & ENGRG UNIV OF IL AT URBANA-CHAMPAIGN ATTN J ECONOMY 1304 W GREEN ST 115B URBANA IL 61801 |

| NO. OF COPIES | ORGANIZATION |
|------------------|---|
| 1 | MISSISSIPPI STATE UNIV DEPT OF AEROSPACE ENGRG ATTN A J VIZZINI MISSISSIPPI STATE MS 39762 |
| 1 | DREXEL UNIV ATTN A S D WANG 3141 CHESTNUT ST PHILADELPHIA PA 19104 |
| 3 | UNIV OF TEXAS AT AUSTIN CAR FOR ELECTROMECHANICS ATTN J PRICE A WALLS J KITZMILLER 10100 BURNET RD AUSTIN TX 78758-4497 |
| 1 | SOUTHWEST RESEARCH INST ENGR & MATL SCIENCES DIV ATTN J RIEGEL 6220 CULEBRA RD PO DRAWER 28510 SAN ANTONIO TX 78228-0510 |
| | <u>ABERDEEN PROVING GROUND</u> |
| 1 | DIRECTOR US ARMY RSCH LABORATORY ATTN AMSRD ARL CI OK TECH LIB BLDG 4600 |
| 1 | US ARMY ATC ATTN CSTE DTC AT AC I W C FRAZER BLDG 400 |
| 1 | DIR USARL ATTN AMSRD ARL CI BLDG |
| 1 | DIR USARL ATTN AMSRD ARL O AP EG M ADAMSON BLDG |
| 1 | DIR USARL ATTN AMSRD ARL SL BB D BELY BLDG 328 |
| 2 | DIR USARL ATTN AMSRD ARL WM J SMITH D LYON BLDG 4600 |

NO. OF
COPIES ORGANIZATION

2 DIR USARL
ATTN AMSRD ARL WM B CHIEF
T KOGLER
BLDG 4600

2 DIR USARL
ATTN AMSRD ARL WM BC P PLOSTINS
J NEWILL
BLDG 390

3 DIR USARL
ATTN AMSRD ARL WM BD B FORCH
R PESCE-RODRIGUEZ B RICE
BLDG 4600

3 DIR USARL
ATTN AMSRD ARL WM BD P CONROY
C LEVERITT A ZIELINSKI
BLDG 390

2 DIR USARL
ATTN AMSRD ARL WM BE R LIEB
M LEADORE
BLDG 4600

1 DIR USARL
ATTN AMSRD ARL WM BF
S WILKERSON
BLDG 390

2 DIR USARL
ATTN AMSRD ARL WM M J MCCAULEY
S MCKNIGHT
BLDG 4600

2 DIR USARL
ATTN AMSRD ARL WM MA
L GHIORSE E WETZEL
BLDG 4600

22 DIR USARL
ATTN AMSRD ARL WM MB
J BENDER T BOGETTI
J BROWN L BURTON
R CARTER K CHO W DE ROSSET
G DEWING R DOWDING
W DRYSDALE R EMERSON
D GRAY D HOPKINS R KASTE
L KECSKES M MINNICINO
B POWERS D SNOHA
J SOUTH M STAKER
J SWAB J TZENG
BLDG 4600

NO. OF
COPIES ORGANIZATION

11 DIR USARL
ATTN AMSRD ARL WM MC J BEATTY
R BOSSOLI E CHIN
S CORNELISON D GRANVILLE
B HART J LASALVIA
J MONTGOMERY F PIERCE
E RIGAS W SPURGEON
BLDG 4600

11 DIR USARL
ATTN AMSRD ARL WM MD P DEHMER
B CHEESEMAN R DOOLEY
G GAZONAS S GHIORSE
M KLUSEWITZ W ROY J SANDS
S WALSH D SPAGNUOLO S WOLF
BLDG 4600

2 DIR USARL
ATTN AMSRD ARL WM RP J BORNSTEIN
C SHOEMAKER
BLDG 1121

1 DIR USARL
ATTN AMSRD ARL WM T B BURNS
BLDG 309

1 DIR USARL
ATTN AMSRD ARL WM TA W GILLICH
BLDG 309

7 DIR USARL
ATTN AMSRD ARL WM TA M BURKINS
B GOOCH T HAVEL C HOPPEL
E HORWATH J RUNYEON
M ZOLTOSKI
BLDG 393

1 DIR USARL
ATTN AMSRD ARL WM TB P BAKER
BLDG 309

1 DIR USARL
ATTN AMSRD ARL WM TC R COATES
BLDG 309

4 DIR USARL
ATTN AMSRD ARL WM TD D DANDEKAR
M RAFTENBERG S SCHOENFELD
T WEERASOORIYA
BLDG 4600

2 DIR USARL
ATTN AMSRD ARL WM TE CHIEF
J POWELL
BLDG 1116A

| <u>NO. OF COPIES</u> | <u>ORGANIZATION</u> |
|--------------------------|--|
| 1 | LTD R MARTIN MERL TAMWORTH RD HERTFORD SG13 7DG UK |
| 1 | CIVIL AVIATION ADMINSTRATION T GOTTESMAN PO BOX 8 BEN GURION INTRNL AIRPORT LOD 70150 ISRAEL |
| 1 | AEROSPATIALE S ANDRE A BTE CC RTE MD132 316 ROUTE DE BAYONNE TOULOUSE 31060 FRANCE |
| 1 | DRA FORT HALSTEAD P N JONES SEVEN OAKS KENT TN 147BP UK |
| 1 | SWISS FEDERAL ARMAMENTS WKS W LANZ ALLMENDSTRASSE 86 3602 THUN SWITZERLAND |
| 1 | DYNAMEC RESEARCH LAB AKE PERSSON BOX 201 SE 151 23 SODERTALJE SWEDEN |
| 1 | ISRAEL INST OF TECHLGY S BODNER FACULTY OF MECHANICAL ENGR HAIFA 3200 ISRAEL |
| 1 | DSTO WEAPONS SYSTEMS DIVISION N BURMAN RLLWS SALISBURY SOUTH AUSTRALIA 5108 AUSTRALIA |

| <u>NO. OF COPIES</u> | <u>ORGANIZATION</u> |
|--------------------------|---|
| 1 | DEF RES ESTABLISHMENT VALCARTIER A DUPUIS 2459 BLVD PIE XI NORTH VALCARTIER QUEBEC CANADA PO BOX 8800 COURCELETTE GOA IRO QUEBEC CANADA |
| 1 | ECOLE POLYTECH J MANSON DMX LTC CH 1015 LAUSANNE SWITZERLAND |
| 1 | TNO DEFENSE RESEARCH R IJSSELSTEIN ACCOUNT DIRECTOR R&D ARMEE PO BOX 6006 2600 JA DELFT THE NETHERLANDS |
| 2 | FOA NATL DEFENSE RESEARCH ESTAB DIR DEPT OF WEAPONS & PROTECTION B JANZON R HOLMLIN S 172 90 STOCKHOLM SWEDEN |
| 2 | DEFENSE TECH & PROC AGENCY GROUND I CREWTER GENERAL HERZOG HAUS 3602 THUN SWITZERLAND |
| 1 | MINISTRY OF DEFENCE RAFAEL ARMAMENT DEVELOPMENT AUTH M MAYSELESS PO BOX 2250 HAIFA 31021 ISRAEL |
| 1 | B HIRSCH TACHKEMONY ST 6 NETAMUA 42611 ISRAEL |

NO. OF
COPIES ORGANIZATION

1 DEUTSCHE AEROSPACE AG
DYNAMICS SYSTEMS
M HELD
PO BOX 1340
D 86523 SCHROBENHAUSEN
GERMANY